

A First Principle Study of Electronic Structure of $\text{In}_2\text{ZnTiO}_6$

Ashwani Kumar^{1,*}, Durga P. Ojha²

¹Department of Physics, National Defence Academy, Khadakwasla, Pune, 410231 MH, India

²P G Department of Physics, Sambalpur University, Jyoti Vihar, Burla, Sambalpur, 768019, India

Abstract The full potential Linearized augmented plane wave (FLAPW) method is employed to study the ground state and crystal properties of $\text{In}_2\text{ZnTiO}_6$. The electronic-energy band structure, site and angular-momentum decomposed density of states and charge-density contours of double perovskite $\text{In}_2\text{ZnTiO}_6$ are calculated by the FLAPW method with the generalized-gradient approximation using density-functional theory. From the analysis of density of states, we conclude that there is hybridization of Ti-d state with the O-p state, which implies that the interaction between the atoms of these two is highly covalent which is consistent with the calculation of electronic band structure as well as charge density studies. The equilibrium values, bulk modulus, and its pressure derivative have been estimated through optimization of the crystal structure of this material.

Keywords Electronic band structure, Density of states, FLAPW

1. Introduction

Double perovskites with general formula $\text{A}_2\text{B}'\text{B}''\text{O}_6$ with A being an alkaline earth such as Ca, Ba, Sr or a lanthanide and B', B'' are the transition metals are a matter of investigation since past decades [1-7]. Kang *et al.* [1] have studied the electronic structure of $\text{Ba}_2\text{FeMoO}_6$ using photoemission spectroscopy. Borges *et al.* [2] investigated the ferromagnetic metallic behaviour of $\text{Ca}_2\text{FeMoO}_6$, $\text{Sr}_2\text{FeMoO}_6$ and $\text{Ba}_2\text{FeMoO}_6$ with curie temperature of 345 – 426 K. Moritomo *et al.* [3-4] shows a strong correlation between the curie temperature and the conductivity at room temperature which implies that the mobile conduction electrons mediate the exchange interaction between the local Fe^{3+} ions. Sarma [5] has pointed out the discrepancies between the manganites and the double perovskites and proposed the mechanism of occurrence of large T_C in double perovskites $\text{Sr}_2\text{FeMoO}_6$. This mechanism has been extended to many other systems by Kanamori and Terakura [6-7]. In this model the hybridization of the Mo 4d (t_{2g}) and Fe 3d (t_{2g}) states plays the key role in stabilizing ferromagnetism at high curie temperatures [5-8]. Based on band calculation using the Local Density approximation (LDA), Pickett [9] has proposed that the double perovskite La_2MnVO_6 can be a promising candidate for exhibiting half-metallic antiferromagnets (HM-AFM) characteristics. The electronic

structure calculations were based on the assumption that both Mn and V ions are trivalent and more importantly a low spin state ($t_{2g}^4 e_g^0$, $S=1$) resulted for all Mn^{3+} ions. Phillip *et al.* [10] studied the effect of structural changes and doping in the double perovskite A_2CrWO_6 (A = Sr, Ba, Ca) on the magnetotransport, the magnetic and optical properties together with band structure calculations. Phillip *et al.* have pointed out that the T_C in double perovskites was discussed to depend sensitively on band structure and band filling in contrast to experimental results [11].

In double perovskites having structural formula $\text{A}_2\text{B}'\text{B}''\text{O}_6$, each transition metal site (B'B'') is surrounded by an oxygen octahedron and the A atoms site are situated in the holes produced by eight adjacent oxygen octahedral. The properties of double perovskite compounds are determined by the relative sizes, valencies and ordering of the A and B site ions.

The study of elemental structures plays a pivotal role in solid-state physics [12]. The structural study gives insight into the properties of the elements. In the present paper, the electronic structure (density of states, band structure) of $\text{In}_2\text{ZnTiO}_6$ (IZT) are calculated by full potential linearized augmented plane wave (FLAPW) method [13] within the generalized gradient approximation (GGA) [14] as the material is a promising candidate for optoelectronic applications.

2. Computational Details

The ground-state properties of IZT are investigated employing the FLAPW method within the generalized

* Corresponding author:

ashwani_kumar04@yahoo.co.in (Ashwani Kumar)

Published online at <http://journal.sapub.org/materials>

Copyright © 2014 Scientific & Academic Publishing. All Rights Reserved

gradient approximation (GGA). The structural parameters of the system were optimized at 2000-k points inside the irreducible Brillouin zone for integration. The full geometrical optimization gives an in-plane lattice constant $a = b = c = 8.0$ and $c/a = 1.0$ of pure $\text{In}_2\text{ZnTiO}_6$. Accurate optimizations of crystal geometries have come to serve as a stringent test for electronic structure calculations. We use our optimized parameters for the study of electronic structure calculations taking muffin tin radius (RMT) as 2.0, 1.9, 1.8 and 1.6 for In, Zn, Ti and O respectively. The total energy has been minimized and calculated with respect to the volume. In our calculation, the crystal structure of IZT has the space group symmetry Fm-3m. The Birch-Murnaghan relation for equation of state (EOS) is used to get the static equilibrium volume V_0 ($=940.39$) as well as the bulk modulus B_0 ($=123.55$ GPa) and its pressure derivative B' ($=3.0873$) at zero pressure.

3. Results and Discussion

In figure 1, we have calculated and minimized the total energy with respect to the volume. In our calculation, the crystal structure of IZT has the space group symmetry

Fm-3m. The Birch-Murnaghan relation for equation of state (EOS) is used to get the static equilibrium volume V_0 ($=940.39$) as well as the bulk modulus B_0 ($=123.55$ GPa) and its pressure derivative B' ($=3.0873$) at zero pressure. The pressure derivative of bulk modulus at zero pressure B'_0 is a parameter of great physical significance in high pressure physics. It is related to a few other important thermo physical properties (like phase transitions, interphase energy, adsorption energy etc.) [14].

The calculated band structure for IZT in the high symmetry direction in the Brillouin zone is shown in figure 2. In this figure, we find a large dispersion of the bands. It can be seen that there are many bands from -3 eV to 1 eV. These bands are mainly contributed from Ti-d and O-p electrons. These bands also overlap each other at and around the Fermi level which indicates that there is hybridization between the Ti-d and O-p states. Comparing it with figure 3, it supports our explanation.

The angular momentum projected densities of states were obtained by using 2000-k points inside the irreducible Brillouin zone for integration. The full geometrical optimization gives an in-plane lattice constant $a = b = c = 8.0$ and $c/a = 1.0$ of pure $\text{In}_2\text{ZnTiO}_6$.

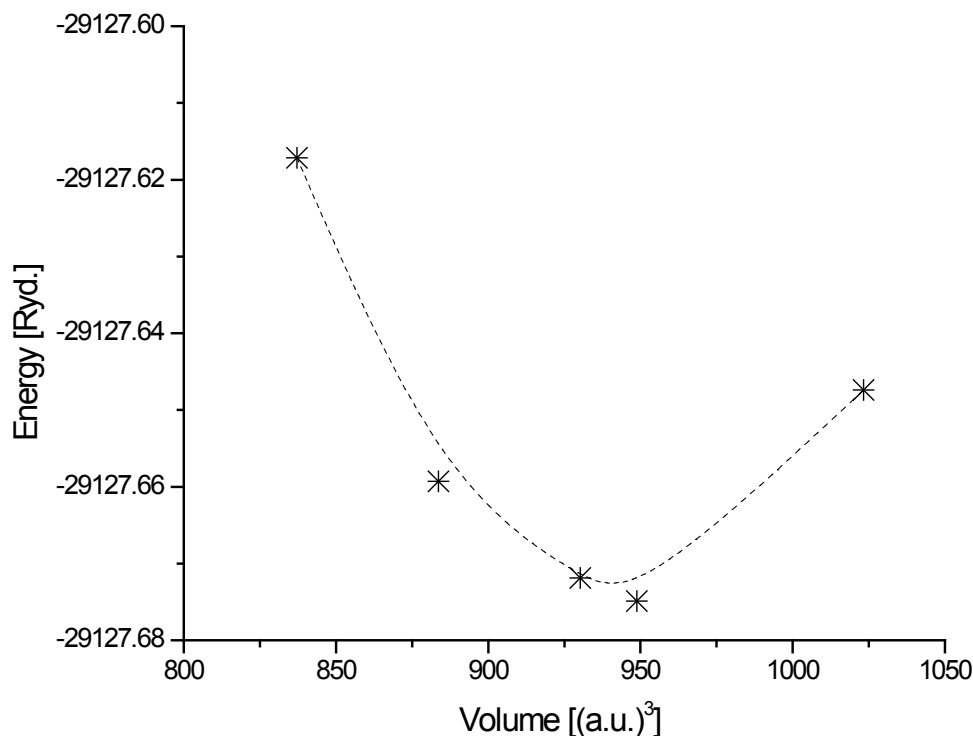


Figure 1. Total Energy of $\text{In}_2\text{ZnTiO}_6$ as a function of cell volume

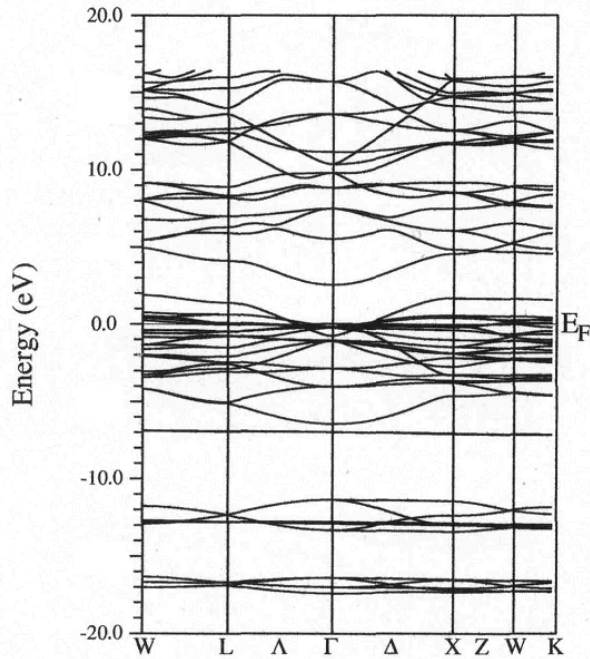


Figure 2. The electronic band structure of $\text{In}_2\text{ZnTiO}_6$ along high symmetry directions

Figure 3 shows the total DOS along with partial DOS of Ti-d and O-p states of IZT. It is observed that the main contribution in the valence band comes from Ti-3d state. The Ti-d state hybridizes with O-p states near Fermi level. The hybridization between Ti-d and O-p states implies that the interaction between the atoms of these two is highly covalent. Titanium has excellent strength to weight ratio, high melting temperature and good corrosion resistance which render it suitable for light-weight, high temperature applications [16]. The tensile and fatigue strength of Ti increase with oxygen content at the cost of compromising ductility and toughness [17, 18]. These changes in mechanical properties are attributed to the interstitial oxygen atoms impeding dislocation motion and suppressing low temperature twinning [19]. Understanding mechanisms underlying this effect of oxygen is thus important from both scientific and industrial points of view.

Figure 4 represents the electron density distribution of $\text{In}_2\text{ZnTiO}_6$ in 100 planes. In figure 4, we can see that the interaction between Ti-d and O-p states is very strong. It implies the strong hybridization between these two states.

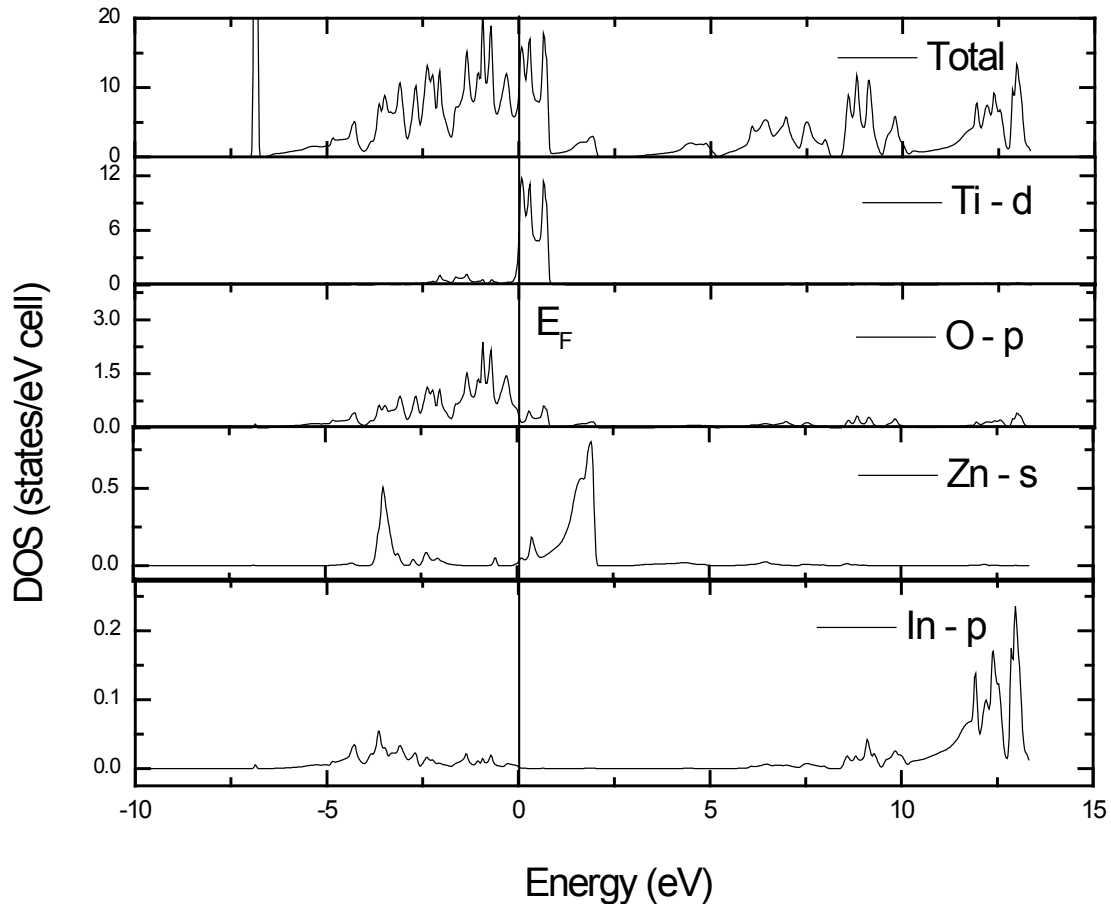


Figure 3. Total DOS and PDOS around Fermi energy of $\text{In}_2\text{ZnTiO}_6$ calculated for the optimized lattice constant

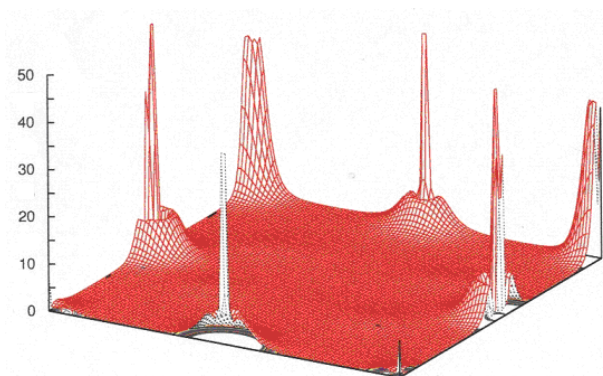


Figure 4. The electron density distribution of IZT in the (100) plane

4. Conclusions

We have performed and analyzed the FLAPW calculation of the double perovskite $\text{In}_2\text{ZnTiO}_6$ (IZT). The ground state and electronic structural properties have been obtained. From the angular momentum projected densities of states at 2000-k points inside the irreducible Brillouin zone for integration, it can be concluded that Ti-d state hybridizes with O-p states near Fermi level and the interaction between the atoms of these two is highly covalent which is further supported by the electron density distribution of $\text{In}_2\text{ZnTiO}_6$ in 100 plane.

ACKNOWLEDGEMENTS

The financial support rendered by the DAE-BRNS, Mumbai, India is gratefully acknowledged.

REFERENCES

- [1] S. M. Metev and V. P. Veiko, *Laser Assisted Microtechnology*, 2nd ed., R. M. Osgood, Jr., Ed. Berlin, Germany: Springer-Verlag, 1998.
- [2] J.-S Kang, H. Han, B W Lee, C G Olson, S W Han, K H Kim, J I Jeong, J H Park and B S Min, 2001, "Electronic structure of the double-perovskite $\text{Ba}_2\text{FeMoO}_6$ using photoemission spectroscopy", *Phys. Rev. B.* 64 024429.
- [3] R P Borges, R M Thomas, C Cullinan, J M D Coey, R Suryanarayanan, L Bendor, L Pinsard-Gaudart and A Revcolevschi, 1999, "Magnetic Properties of the double perovskites A_2FeMoO_6 ; A = Ca, Sr, Ba" *J. Phys. Condens. Matter* 11 1445.
- [4] Y Moritomo, Sh Xu, A Machida, T Akimoto, E Nishibori, M Takata and M Sakata, 2000, "Electronic structure of double-perovskite transition-metal oxides", *Phys. Rev. B.* 61 R7827.
- [5] Y Moritomo, Sh Xu, T Akimoto, A Machida, N Hamada, K Ohoyama, E Nishibori, M Takata and M Sakata, 2000, "Electron doping effects in conducting $\text{Sr}_2\text{FeMoO}_6$ ", *Phys. Rev. B.* 62 14224.
- [6] D D Sarma, P Mahadevan, T Saha-Dasgupta, Sugata Ray, and A Kumar, 2000, "Electronic Structure of $\text{Sr}_2\text{FeMoO}_6$ ", *Phys. Rev. Lett.* 85, 2549.
- [7] J Kanamori and K Terakura, 2001, "A general mechanism underlying ferromagnetism in transition metal compounds", *J. Phys. Soc. Jpn.* 70 1433.
- [8] Z Fang, K Terakura and J Kanamori, 2001, "Strong ferromagnetism and weak antiferromagnetism in double perovskites: W, and Re)", *Phys. Rev. B* 63 180407 (R).
- [9] D D Sarma, P Mahadevan, T Saha-Dasgupta, Sugat Ray and A Kumar, 2001, "A new class of magnetic materials: $\text{Sr}_2\text{FeMoO}_6$ and related compounds" *Solid State Mat. Sci.* 5, 261.
- [10] Warren E Pickett, 1998, "Spin-density-functional-based search for half-metallic antiferromagnets" *Phys. Rev. B.* 57 10613.
- [11] J B Phillip, P Majewski, L Alff, A Erb, R Gross, T Graf, M S Brandt, J Simon, T Walther, W Mader, D Topwal and D D Sarma, 2003, "Structural and doping effects in the half-metallic double perovskite A_2CrWO_6 (A= Sr, Ba, Ca) *Phys. Rev. B.* 68 144431.
- [12] K Phillips, A Chattopadhyay and A J Millis, 2003, "Dynamical mean-field theory of double perovskite ferrimagnets", *Phys. Rev. B.* 67 125119.
- [13] S Lee, R Rousseau and Cyndi Wells, 1992, "Optimization of the main-group and late-transition-metal elemental structures: Gallium, boron, zinc, cadmium, and manganese" *Phys. Rev. B.* 46 12121.
- [14] P Blaha, K Schwarz, G Madsen, D Kvasnicka and J Luitz, 2001, *WIEN 2K, An Augmented Plane Wave + Local Orbitals Program for Calculating Crystal Properties* (Karlheinz Schwarz, Techn. Universitat Wien, Austria), 2001. ISBN 3 – 950103 1 – 1 – 2.
- [15] J P Perdew, J A Chevary, S H Vosko, K A Jackson, M R Perdoso, D J Singh and C Fiolhais, 1992, "Atoms, molecules, solids, and surfaces: Applications of the generalized gradient approximation for exchange and correlation" *Phys. Rev. B.* 46 6671.
- [16] M. Long and H. Rack, 1998, "Titanium Alloys in Total Joint Replacement – A materials science perspective" *Biomaterials* 19, 1621.
- [17] M. Wasz, F. Brotzen, R. McLellan, and A. Griffin, 1996, "Effect of Oxygen and Hydrogen on mechanical properties of commercial purity Titanium" *International Materials Review* 41, 1.
- [18] G. L'utjering and J. C. Williams, *Titanium*, 2nd ed., Engineering Materials and Processes (Springer Berlin Heidelberg, 2007).
- [19] H. Conrad, 1981, "Effect of Interstitial Solutes on the Strength and Ductility of Titanium" *Prog. Mater. Sci.* 26, 123.